


Aluminum standards and data

| 2013 |

The Aluminum Association

Incorporated

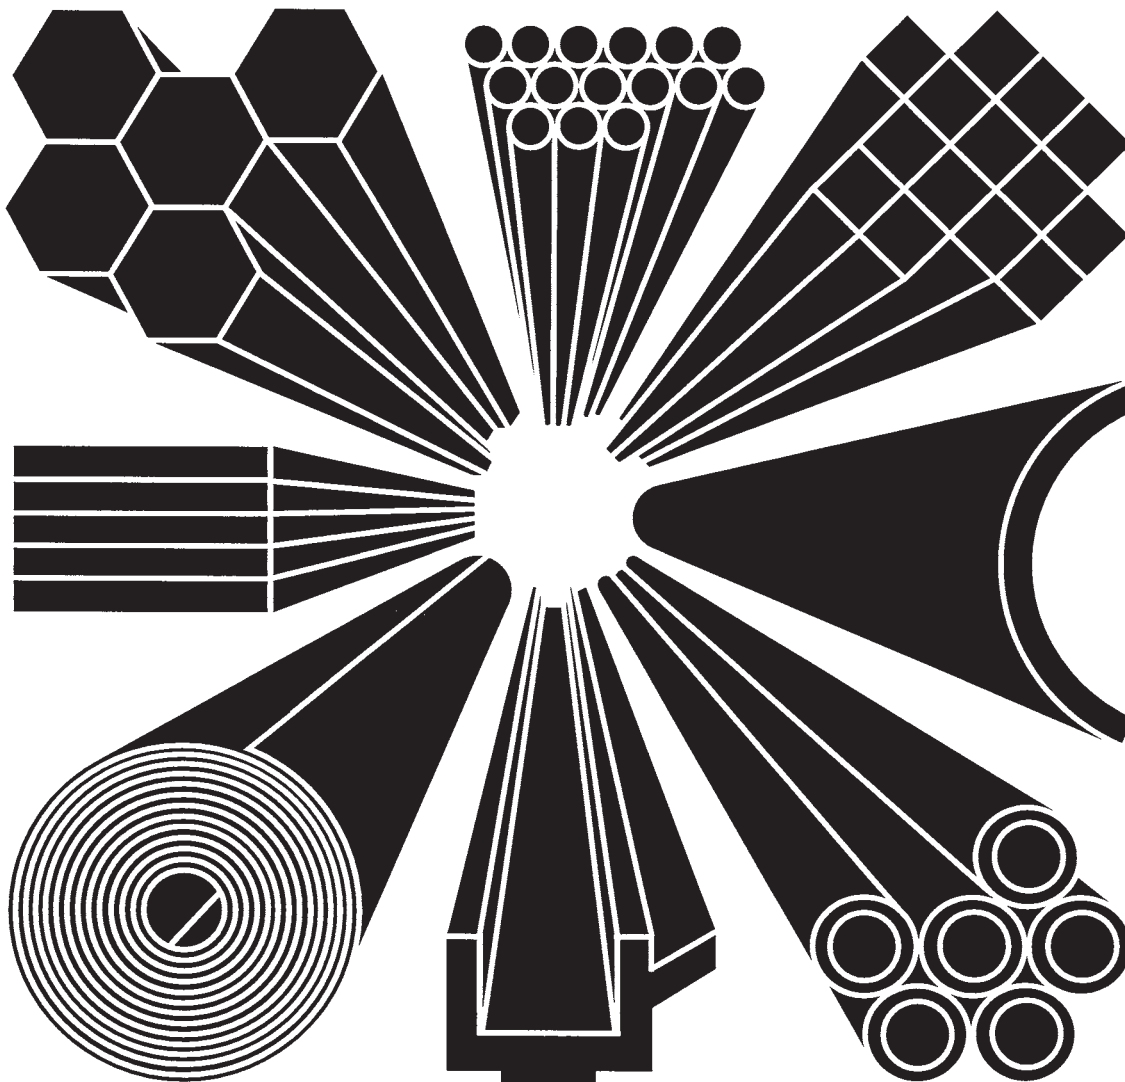

This is a preview of "AA ASD". [Click here to purchase the full version from the ANSI store.](#)

CONTENTS

	Page		Page
1. GENERAL INFORMATION		8. FIN STOCK	
Characteristics	1-1	Introduction	8-1
Alloy and temper designations	1-3	Mechanical property limits	8-2
Metallurgical aspects	1-11	Tolerances	8-2
Nominal chemical compositions	1-13	9. FOIL	
AA wrought alloys and similar foreign alloys	1-15	Introduction	9-1
Specification cross reference	1-17	Unmounted	9-2
Mill product specifications	1-23	Laminated	9-3
2. TYPICAL PROPERTIES		Printed	9-4
Typical mechanical properties	2-1	10. WIRE, ROD AND BAR—ROLLED OR COLD FINISHED	
Typical tensile properties at various temperatures	2-5	Introduction	10-1
Typical physical properties	2-10	Mechanical property limits	
Density calculation procedure	2-12	Non-heat-treatable alloys	10-3
Nominal densities	2-14	Heat-treatable alloys	10-5
3. APPLICATION AND FABRICATION		Rivet and cold heading wire and rod	10-6
Wrought alloy products and tempers	3-1	Computation of weight per foot	10-6
Specialty mill products	3-7	Tolerances	10-7
Comparative characteristics and applications	3-8	11. WIRE, ROD, BAR AND PROFILES—EXTRUDED	
Typical heat treatments	3-12	Introduction	11-1
Typical annealing treatments	3-17	Mechanical property limits	11-2
4. QUALITY CONTROL		Tolerances	11-6
Sampling and testing	4-1	12. TUBE AND PIPE	
Tension testing of foil	4-4	Introduction	12-1
Visual inspection	4-5	Extruded tube	
Ultrasonic inspection	4-6	Mechanical property limits	12-3
Identification marking	4-7	Tolerances	12-6
Rivet identification markings	4-12	Extruded coiled tube	
Color code	4-13	Mechanical property limits	12-11
Handling and storing aluminum	4-14	Tolerances	12-11
Protective oil	4-14	Drawn tube	
Certification documentation	4-15	Mechanical property limits	12-12
Appendix 1—Test specimen location	4-16	Tolerances	12-15
Appendix 2—Tolerances	4-18	Heat-exchanger tube	12-18
5. TERMINOLOGY	5-1	Welded tube	12-20
6. STANDARDS SECTION		Pipe	
Limits	6-1	Mechanical property limits	12-21
Components of clad products	6-4	Tolerances	12-22
Chemical composition limits	6-5	Diameters, wall thicknesses, weights	12-23
Ultrasonic discontinuity limits	6-7	Rigid electrical conduit	12-25
Acceptance criteria for corrosion	6-7	13. STRUCTURAL PROFILES	
Location for electrical conductivity measurements	6-9	Introduction	13-1
Fracture toughness limits	6-9	Mechanical property limits	13-3
Corrosion test criteria	6-10	Aluminum Association channels and I-beams	13-4
7. SHEET AND PLATE		American standard profiles	13-5
Introduction	7-1	14. FORGING STOCK	
Mechanical property limits		Introduction	14-1
Non-heat-treatable alloys	7-3	Mechanical property limits	14-1
Heat-treatable alloys	7-12	Tolerances	14-2
Brazing sheet	7-22		
Weights per square foot	7-23		
Weight conversion factors	7-24		
Recommended bend radii for 90-degree cold bend	7-24		
Tolerances	7-26		
Painted sheet	7-31		
Commercial roofing and siding	7-34		
Duct sheet	7-36		
Tread plate	7-37		

15. FORGINGS		16. ELECTRIC CONDUCTORS	
Introduction	15-1	Introduction	16-1
Die forgings		Mechanical and physical property limits	16-3
Mechanical property limits	15-2	Equivalent resistivity values	16-4
Hand forgings		Bend properties of bus bar	16-5
Mechanical property limits	15-3	Tolerances	16-6
Tolerances	15-6		
Rolled rings		INDEX	17-1
Mechanical property limits	15-6		

Abbreviations Used in This Manual

ACSR	aluminum cable steel reinforced	ksi	thousand pounds per square inch or kips per square inch
BHN	Brinell hardness number	lb	pound
Btu	British thermal unit	max	maximum
cu	cubic	MHZ	megahertz
diam, D	diameter	mil	circular mil = 0.001 in.
dim.	dimension	min	minimum
°F	degree Fahrenheit	mm	millimeter
ft	foot	O.D.	outside diameter
hr	hour	psi	pounds per square inch
IACS	International Annealed Copper Standard	sq	square
I. D.	inside diameter		
in.	inch		
kip	thousand pounds		

Other uses of single and combined letters (A, B, D, Y, AA, etc.) can be found in this publication. They represent linear measurements, radii, angles, and so forth, as shown on diagrams, formulas, and so on, contained in tables and shown as specific to that table.

Introduction

This manual contains useful information and data pertaining to chemical composition limits, mechanical and physical properties, tolerances and other characteristics of various aluminum and aluminum alloy wrought products. The content of the manual is subject to periodic revision to keep abreast of advances in production methods, to add data on new alloys and products, and to delete those that become inactive or whose usage becomes limited.

The criteria for adding or deleting alloy-tempers:

1. The alloy shall have been registered in accordance with the rules shown in the foreword to the "Registration Record of Aluminum Association Designations and Chemical Composition Limits for Wrought Aluminum and Wrought Aluminum Alloys."
2. The temper shall have been registered as an Aluminum Association Technical Division (AATD) registration in accordance with the rules shown in the registration listing, "Tempers for Aluminum and Aluminum Alloy Products."
3. Entries shall be available for inclusion in all tables in Sections 1, 2, 3, 4, 6 and the applicable tolerance tables, unless the Technical Committee on Product Standards of The Aluminum Association considers some of the entries unnecessary or inappropriate.
4. Alloy-tempers shall be deleted when they become inactive or when their usage becomes limited.
5. All inclusions in or removals from ASD shall have been approved by formal ballot of the Technical Committee on Product Standards of The Aluminum Association.

Complete revision of the manual is customarily accomplished on a triennial basis. Important changes, additions or deletions that occur between issues are recorded in Addenda that may be published at appropriate intervals. Individual suppliers should be contacted for information concerning effectivity of changes included in the Addenda. This edition supersedes all previous editions and addenda.

The first three sections of the manual (blue pages) contain information of a general nature that may be useful in comparing materials. The typical properties and characteristics listed are not guaranteed and should not be used for design purposes. The fourth section (blue pages) contains information relating to testing, inspection and identification and the fifth section (yellow pages) lists the definitions of many terms used in the wrought aluminum industry. The remaining twelve sections (white pages) comprise chemical composition limits, mechanical property limits, dimensional tolerances and other data classified by product form.

Since a completely metric (SI) version is now available, the only metric values shown are those that have been customarily used.

Several typographical errors have been corrected from the previous edition. Vertical bars have been inserted in the margins to help the reader identify technical revisions. These revisions are summarized chronologically on the following pages:

Chronological Summary of Changes to the 2009 Edition of Aluminum Standards and Data		
DATE	PAGE (TABLE/PARAGRAPH)	DESCRIPTION OF CHANGE
13-11-13	12-10	Deleted test method of Interneral Cleanliness and revised the requirement section.
13-10-23	4-13	Added Color Code for Alloy 7185
13-10-18	1-3 (Section 2)	Revised the placement of footnote references (2, 3 and 4) and added footnote reference "13" to the heading
13-10-18	1-3 (Section 2, Paragraph 2)	Deleted word "national" and changed "will" to "shall"
13-10-18	1-3	Added footnote "13"
13-10-18	1-4 (Section 2.2, Paragraph 1)	Added wording "original alloy and"
13-10-18	1-4 (Section 2.2)	Deleted word "national" from the last paragraph
13-10-18	1-4 (Section 2.4)	Deleted word "national" from section heading
13-10-18	1-4 (Section 2.4, Paragraph 1)	Deleted "national", "by another country" and "internationally"; and changed "following" to "after"
13-10-18	1-4 (Section 2.4, Paragraph 2)	Deleted "national" and "registered by another country"
13-10-18	1-4	Modified the placement of comma in footnote 5
13-10-18	1-5 (Section 2.4)	Changed "Different" to "change in" in parts "c" and "d"
13-10-18	1-5 (Section 2.4)	Changed "on" to "of" and added wording "expressed singly or as a combination" to part "c"
13-10-18	1-5 (Section 2.4)	Modified the last paragraph
13-10-18	1-5 (Section 3)	Revised the placement of footnote references (2, 3 and 4)
13-10-18	1-8 (Section 4.3)	Modified first paragraph
13-10-18	1-10	Modified appendix "A3" to add sections A3.1 and A3.2; and added temper designation "O2"
13-03-08	12-7 (12.4)	Revised Column 6, Eccentricity
13-03-08	12-7 (12.5)	Revised Column 5, Eccentricity
13-03-05	1-8	Addition of a definition for H1_8
12-10-25	5-5	Changed "Hard Conversion" to "Substitution" and modified definition
12-10-25	5-5	Changed "Soft Conversion" to "Conversion" and modified definition
12-09-11	4-13	Added Color Code for Alloy 7136
12-09-10	7-12 (7.2)	Deactivated Mechanical Property Limits for Alclad 2014-O Sheet and Plate over 0.500 inch
12-09-10	7-12 (7.2)	Deactivated Mechanical Property Limits to Alclad 2014-T451 Plate over 0.500 inch
12-09-10	7-12 (7.2)	Deactivated Mechanical Property Limits to Alclad 2014-T42 Sheet and Plate over 0.500 inch
12-09-10	7-12 (7.2)	Deactivated Mechanical Property Limits to Alclad 2014-T62 and T651 Plate over 0.500 inch
12-09-10	7-16 (7.2)	Deactivated Mechanical Property Limits to Alclad 2219-O Sheet and Plate over 0.500 inch
12-09-10	7-16 (7.2)	Deactivated Mechanical Property Limits to Alclad 2219-T62 Sheet and Plate over 0.500 inch
12-09-10	7-17 (7.2)	Deactivated Mechanical Property Limits to Alclad 6061-O Sheet and Plate over 0.500 inch
12-09-10	7-17 (7.2)	Deactivated Mechanical Property Limits to Alclad 6061-T451 Plate over 0.500 inch
12-09-10	7-17 (7.2)	Deactivated Mechanical Property Limits to Alclad 6061-T42 Sheet and Plate over 0.500 inch
12-09-10	7-17 (7.2)	Deactivated Mechanical Property Limits to Alclad 6061-T62 and T651 Plate over 0.500 inch
12-09-10	7-18 (7.2)	Deactivated Mechanical Property Limits to Alclad 7075-O Sheet and Plate over 0.500 inch
12-09-10	7-18 (7.2)	Deactivated Mechanical Property Limits to Alclad 7075-T62 and T651 Plate over 0.500 inch
12-09-10	7-18 (7.2)	Deactivated Mechanical Property Limits to Alclad 7075-T7351 Plate over 0.500 inch
12-09-10	7-19 (7.2)	Deactivated Mechanical Property Limits to Alclad 7075-T7651 Plate over 0.500 inch

Chronological Summary of Changes to the 2009 Edition of Aluminum Standards and Data		
DATE	PAGE (TABLE/PARAGRAPH)	DESCRIPTION OF CHANGE
12-09-10	7-19 (7.2)	Deactivated Mechanical Property Limits to 2 1/2% Alclad 7075-O Sheet and Plate over 0.500 inch
12-09-10	7-19 (7.2)	Deactivated Mechanical Property Limits to 2 1/2% Alclad 7075-T62 and T651 Plate over 0.500 inch
12-09-10	7-19 (7.2)	Deactivated Mechanical Property Limits to 2 1/2% Alclad 7075-T7351 Plate over 0.500 inch
12-09-10	7-19 (7.2)	Deactivated Mechanical Property Limits to 2 1/2% Alclad 7075-T7651 Plate over 0.500 inch
12-09-10	7-19 (7.2)	Deactivated Mechanical Property Limits to Alclad One Side 7075-O Sheet and Plate over 0.500 inch
12-09-10	7-19 (7.2)	Deactivated Mechanical Property Limits to Alclad One Side 7075-T62 and T651 Plate over 0.500 inch
12-09-10	7-19 (7.2)	Deactivated Mechanical Property Limits to 2 1/2% Alclad 7075-O Sheet and Plate over 0.500 inch
12-09-10	7-19 (7.2)	Deactivated Mechanical Property Limits to 2 1/2% Alclad One Side 7075-T62 and T651 Plate over 0.500 inch
12-07-18	1-14 (1.1)	Added Nominal Chemical Composition for 6360, and added footnote 12 and definition
12-07-18	1-21 (1.3)	Added 6360 Extrusions Specification Cross Reference
12-07-18	1-23 (1.4)	Added 6360 Extrusions to ASTM B221
12-07-18	2-3 (2.1)	Added 6360-T5 and -T6
12-07-18	2-8 (2.2)	Added 6360-T5 and -T6
12-07-18	2-11 (2.3)	Added 6360-T5 and -T6
12-07-18	2-14 (2.4)	Added 6360
12-07-18	3-5 (3.1)	Added 6360-T5 and -T6 Extrusions
12-07-18	3-10 (3.3)	Added 6360-T5 and -T6 Extrusions
12-07-18	3-14 (3.4)	Added 6360-T5 and -T6 Extrusions
12-07-18	3-17 (3.5)	Added 6360 Alloy
12-07-18	4-13	Added Color Code for Alloy 6360
12-07-18	6-6 (6.2)	Added 6360 Composition Limits
12-07-18	11-3 (11.1)	Added 6360-T5 and -T6 Extrusions
12-07-18	12-5 (12.1)	Added 6360-T5 and -T6 Extrusions
12-06-28	3-16 (3.4)	Revised definition for footnote 2
12-06-20	4-7	Revised Identification Marking section
12-06-20	4-8	Revised Identification Marking section
12-06-20	4-9	Revised Identification Marking section
12-06-20	4-10	Revised Typical Identification Marking Figure 4.1
12-06-20	4-11	Revised Typical Identification Marking Figure 4.1
12-06-12	7-9 (7.1)	Added Max UTS Limits to H116 Tempers
12-06-12	7-10 (7.1)	Added Max UTS Limits to H116 Tempers
12-06-08	4-13	Assignment of Color Codes for 2060 and 2099 in ASD Quality Control Section
12-06-04	11-5	Correction to footnote 14 for table 11.1
12-06-04	12-5	Correction to footnote 7 for table 12.1
12-05-30	12-13 (12.19)	Correction to Alloy/Temper number
12-05-08	3-14 (3.4)	Replaced footnote 13 with footnote 15 for 6063-T4 Extruded Rod, Bar, Profiles & Tube
12-04-27	6-8 (6.4)	Modified footnote 7
12-04-16	13-4 (13.3)	Realigned line under Section Properties
12-03-29	7-27 (7.10)	Correction to table heading
12-03-22	12-16 (12.22)	Insertion of minus sign in Tolerance columns
12-03-21	5-2	Modified definition for Combination
12-03-21	5-2	Modified definition for Interference Color
12-01-31	5-3	Modified definition for Billet
12-01-31	5-16	Added definition for Product, Semi-finished

Chronological Summary of Changes to the 2009 Edition of Aluminum Standards and Data		
DATE	PAGE (TABLE/PARAGRAPH)	DESCRIPTION OF CHANGE
12-01-31	5-16	Added definition for Product, Unwrought
12-01-31	5-16	Added definition for Product, Wrought
12-01-31	5-18	Added definition for Semi-finished Product
12-01-31	5-23	Added definition for Unwrought Product
12-01-31	5-24	Relocated definition for Wrought Product
11-12-30	10-7 (10.9)	Correction to width listed for 1.501-2.000 gauge range
11-12-01	2-12	Modified the first paragraph to add "nominal and weight" in second sentence
11-09-13	12-6 (12.2)	Revised table header
11-07-15	4-13	Deleted alloys 2111 and 5554 in table of color codes
11-06-24	4-13	Assigned color codes to alloys 2040 and 7085 in table of color codes
11-06-14	1-23 (1.4)	Added AMS 2770
11-06-14	3-16 (3.4)	Revised footnote 2, to replace ASTM B597 (cancelled) with ASTM B918
11-06-10	12-21 (12.48)	Modified column header and added footnotes 7 and 8
11-06-10	12-22 (12.49)	Modified column header and added footnotes 7 and 8
11-06-10	12-22 (12.49)	Changed pipe size from 5-7 to 5-6
11-06-10	12-22 (12.53)	Modified column header and added footnote 7 and 8
11-06-10	12-23 (12.55)	Modified column header to add footnote 5
11-06-10	12.24 (12.55)	Modified column header and added footnote 5
11-03-24	7-30 (7.18)	Added T7451 Temper to footnote 2
11-03-05	6-6 (6.2)	Revision to footnote 2
11-02-18	1-14 (1.1)	Deleted Alloy 7178
11-02-18	1-22 (1.3)	Deleted Alloy 7178 & Alclad 7178
11-02-18	1-23 (1.4)	Deleted Alloy 7178 & Alclad 7178
11-02-18	1-25 (1.4)	Deleted referenced spec for Alloy 7178 & Alclad 7178
11-02-18	2-4 (2.1)	Deleted Alloy 7178 & Alclad 7178
11-02-18	2-9 (2.2)	Deleted Alloy 7178
11-02-18	2-11 (2.3)	Deleted Alloy 7178
11-02-18	2-14 (2.4)	Deleted Alloy 7178
11-02-18	3-6 (3.1)	Deleted Alloy 7178 & Alclad 7178
11-02-18	3-10 (3.3)	Deleted Alloy 7178
11-02-18	3-16 (3.4)	Deleted Alloy 7178 and revised footnote 27
11-02-18	3-17 (3.5)	Deleted Alloy 7178
11-02-18	4-13	Deleted Alloy 7178
11-02-18	6-4 (6.1)	Deleted Alclad 7178 S&P
11-02-18	6-6 (6.2)	Deleted Alloy 7178
11-02-18	6-7 (6.3)	Deleted Alloy 7178
11-02-18	6-8 (6.4)	Deleted Alloy 7178
11-02-18	6-9 (6.5)	Deleted Alloy 7178
11-02-18	6-10 (6.7)	Deleted Alloy 7178
11-02-18	7-20 (7.2)	Deleted Alloy 7178 & Alclad 7178
11-02-18	7-24 (7.5)	Deleted Alloy 7178
11-02-18	7-25 (7.6)	Deleted Alloy 7178
11-02-18	7-26 (7.7b)	Deleted Alloy 7178
11-02-18	10-6 (10.3)	Deleted Alloy 7178
11-02-18	10-6 (10.4)	Deleted Alloy 7178
11-02-18	11-4 (11.1)	Deleted Alloy 7178
10-12-14	1-8	Repositioned the Appendix heading
10-12-14	1-8	Correction to definitions listed for H116 and H321

Chronological Summary of Changes to the 2009 Edition of Aluminum Standards and Data		
DATE	PAGE (TABLE/PARAGRAPH)	DESCRIPTION OF CHANGE
10-11-29	3-6 (3.1)	Revision to Footnote 2
10-11-23	2-3 (2.1)	Deleted Alloy 6101-H111
10-11-23	3-5 (3.1)	Deleted Alloy 6101-H111
10-11-23	16-4 (16.3)	Deleted Alloy 6101-H111
10-11-23	16-5 (16.5)	Deleted Alloy 6101-H111
10-11-03	2-11 (2.3)	Correction to Footnote 1
10-09-24	1-14 (1.1)	Deleted Alloy 7008
10-09-24	2-14 (2.4)	Deleted Alloy 7008
10-09-24	3-6 (3.1)	Deleted Alloy 7008
10-09-24	6-4 (6.1)	Deleted Alloy 7008
10-09-24	6-6 (6.2)	Deleted Alloy 7008
10-09-24	7-19 (7.2)	Deleted Alloy 7008
10-08-19	11-3 (11.1)	Added footnote 15 to 6082-T6, T6511
10-08-19	11-5	Added definition for footnote 15
10-08-09	12-5 (12.1)	Added footnote 8 to 6082-T6
10-08-09	12-5	Added definition for footnote 8
10-07-28	7-5 (7.1)	Correction to min Yield Strength from 9 to 9.0 for Alclad 3003-H112
10-07-28	7-6 (7.1)	Correction to min Yield Strength from 26.0 to 25.5 for 3005-H27
10-07-28	7-14 (7.2)	Correction to min Ultimate Strength from 63 to 63.0 for 1 ^{1/2} Alclad 2024-T3
10-05-18	iii	Revision to Define "AATD"
10-02-02	1-13 (1.1)	Deleted Alloy 5652
10-02-02	1-23 (1.4)	Deleted Alloy 5652 From SB-209, B209, B241
10-02-02	2-3 (2.1)	Deleted Alloy 5652
10-02-02	2-3 (2.1)	Corrected Alloy/Temper 5456-H25 to 5456-H112
10-02-02	2-8 (2.2)	Deleted Alloy 5652
10-02-02	2-10 (2.3)	Deleted Alloy 5652
10-02-02	2-14 (2.4)	Deleted Alloy 5652
10-02-02	3-4 (3.1)	Deleted Alloy 5652
10-02-02	3-9 (3.3)	Deleted Alloy 5652
10-02-02	3-17 (3.5)	Deleted Alloy 5652
10-02-02	6-5 (6.2)	Deleted Alloy 5652
10-02-02	7-10 (7.1)	Deleted Alloy 5652
10-02-02	7-20 (7.2)	Correction to Alclad 7475-T61 Sheet, Tensile Yield Strength
10-02-02	7-20 (7.2)	Correction to Alclad 7475-T761 Sheet, Specified Thickness and Tensile Yield Strength
10-02-02	7-24 (7.5)	Deleted Alloy 5652
10-02-02	7-25 (7.6)	Deleted Alloy 5652
10-02-02	7-29 (7.17)	Deleted Alloy 5652
09-11-17	2-12 & 2-13	Modifications to the Density Calculation Procedure
09-09-25	5-1	Corrected spelling in Alclad definition section
09-09-08	6-9 (6.6)	Footnote 5, Corrected width to read W=0.25
09-07-29	7-10 (7.1)	Reinstated Missing Alloy/Temper 5254-H32
09-07-10	2-8 (2.2)	Correction to Elongation of 6063-T5 at 75 °F

**Chronological Summary of Changes to the
2009 Edition of Aluminum Standards and Data**

The data contained in this manual reflect a consensus of those substantially concerned with its development. The data are intended as a guide to aid the manufacturer, the consumer, and the general public. The existence of the data does not in any respect preclude anyone, whether he has approved the data or not, from manufacturing, marketing, purchasing, or using products, processes, or procedures not conforming to the data. Producers of goods made in conformity with the data contained herein are encouraged on their own responsibility to state in advertising, promotion material, or on tags or labels, that the goods are produced in conformity with the data contained herein, including any ANSI standards incorporated in the manual.

The Aluminum Association has used its best efforts in compiling the information contained in this book. Although the Association believes that its compilation procedures are reliable, it does not warrant, either expressly or impliedly,

the accuracy or completeness of this information. The Aluminum Association assumes no responsibility or liability for the use of the information herein.

Some of the registered alloys or tempers may be the subject of a U.S. patent or patent application, and their listing herein is not to be construed in any way as the granting of a license under such patent rights.

All Aluminum Association published standards, data, specifications and other material are reviewed at least every five years and revised, reaffirmed or withdrawn.

Users are advised to contact The Aluminum Association to ascertain whether the information in this publication has been superseded in the interim between publication and proposed use.

1. General Information

A unique combination of properties makes aluminum one of our most versatile engineering and construction materials. A mere recital of its characteristics is impressive. It is light in mass, yet some of its alloys have strengths greater than that of structural steel. It has high resistance to corrosion under the majority of service conditions, and no colored salts are formed to stain adjacent surfaces or discolor products with which it comes into contact, such as fabrics in the textile industry and solutions in chemical equipment. It has no toxic reaction. It has good electrical and thermal conductivities and high reflectivity to both heat and light. The metal can easily be worked into any form and readily accepts a wide variety of surface finishes.

Lightness is one of aluminum's most useful characteristics. The specific gravity is about 2.7. The mass ("weight") of aluminum is roughly 35 percent that of iron and 30 percent that of copper.

Commercially pure aluminum has a tensile strength of about 13,000 pounds per square inch. Thus its usefulness as a structural material in this form is somewhat limited. By working the metal, as by cold rolling, its strength can be approximately doubled. Much larger increases in strength can be obtained by alloying aluminum with small percentages of one or more other elements such as manganese, silicon, copper, magnesium or zinc. Like pure aluminum, the alloys are also made stronger by cold working. Some of the alloys are further strengthened and hardened by heat treatments so that today aluminum alloys having tensile strengths approaching 100,000 pounds per square inch are available.

A wide variety of mechanical characteristics, or tempers, is available in aluminum alloys through various combinations of cold work and heat treatment. In specifying the temper for any given product, the fabricating process and the amount of cold work to which it will subject the metal should be kept in mind. In other words, the temper specified should be such that the amount of cold work the metal will receive during fabrication will develop the desired characteristics in the finished products.

Aluminum and its alloys lose part of their strength at elevated temperatures, although some alloys retain good strength at temperatures from 400°F to 500°F. At subzero temperatures, however, their strength increases without loss of ductility, so that aluminum is a particularly useful metal for low-temperature applications.

When aluminum surfaces are exposed to the atmosphere, a thin invisible oxide skin forms immediately, which protects the metal from further oxidation. This self-protecting characteristic gives aluminum its high resistance to corrosion. Unless exposed to some substance or condition that destroys this protective oxide coating, the metal remains fully protected against corrosion. Aluminum is highly resistant to weathering, even in industrial atmospheres that often corrode other metals. It is also corrosion resistant to many acids. Alkalis are among the few substances that attack the oxide skin and therefore are corrosive to aluminum. Although the metal can safely be used in the presence of certain mild alkalis with the aid of inhibitors, in general, direct contact with alkaline substances should be avoided.

Some alloys are less resistant to corrosion than others, particularly certain high-strength alloys. Such alloys in some forms can be effectively protected from the majority of corrosive influences, however, by cladding the exposed surface or surfaces with a thin layer of either pure aluminum or one of the more highly corrosion-resistant alloys.

A word of caution should be mentioned in connection with the corrosion-resistant characteristics of aluminum. Direct contacts with certain other metals should be avoided in the presence of an electrolyte; otherwise galvanic corrosion of the aluminum may take place in the vicinity of the contact area. Where other metals must be fastened to aluminum, the use of a bituminous paint coating or insulating tape is recommended.

The fact that aluminum is nontoxic was discovered in the early days of the industry. It is this characteristic that permits the metal to be used in cooking utensils without any harmful effect on the body, and today we find also a great deal of aluminum equipment in use by food processing industries. The same characteristic permits aluminum foil wrapping to be used safely in direct contact with food products.

Aluminum is one of the two common metals having an electrical conductivity high enough for use as an electric conductor. The conductivity of electric conductor grade (1350) is about 62 percent that of the International Annealed Copper Standard. Because aluminum has less than one-third the specific gravity of copper, however, a pound of aluminum will go about twice as far as a pound of copper when used for this purpose. Alloying lowers the conductivity somewhat, so that wherever possible alloy 1350 is used in electric conductor applications.

The high thermal conductivity of aluminum came prominently into play in the very first large-scale commercial application of the metal in cooking utensils. This characteristic is important wherever the transfer of thermal energy from one medium to another is involved, either heating or cooling. Thus aluminum heat exchangers are commonly used in the food, chemical, petroleum, aircraft and other industries. Aluminum is also an excellent reflector of radiant energy through the entire range of wavelengths, from ultraviolet, through the visible spectrum to infrared and heat waves, as well as electromagnetic waves of radio and radar.

Aluminum has a light reflectivity of over 80 percent, which has led to its wide use in lighting fixtures. Aluminum roofing reflects a high percentage of the sun's heat, so that buildings roofed with this material are cooler in summer.

The ease with which aluminum may be fabricated into any form is one of its most important assets. Often it can compete successfully with cheaper materials having a lower degree of workability. The metal can be cast by any method known to foundrymen; it can be rolled to any desired thickness down to foil thinner than paper; aluminum sheet can be stamped, drawn, spun or roll-formed. The metal also may be hammered or forged. Aluminum wire, drawn from rolled rod, may be stranded into cable of any desired size and type. There is almost no limit to

the different profiles in which the metal may be extruded.

The ease and speed with which aluminum may be machined is one of the important factors contributing to the low cost of finished aluminum parts. The metal may be turned, milled, bored, or machined in other manners at the maximum speeds of which the majority of machines are capable. Another advantage of its flexible machining characteristics is that aluminum rod and bar may readily be employed in the highspeed manufacture of parts by automatic screw machines.

Almost any method of joining is applicable to aluminum: riveting, welding, brazing or soldering. A wide variety of mechanical aluminum fasteners simplifies the assembly of many products. Adhesive bonding of aluminum parts is widely employed, particularly in joining aircraft components.

For the majority of applications, aluminum needs no protective coating. Mechanical finishes such as polishing, sand blasting or wire brushing meet the majority of needs. In many instances, the surface finish supplied is entirely adequate without further finishing. Where the plain aluminum surface does not suffice, or where additional protection is required, any of a wide variety of surface finishes may be applied. Chemical, electrochemical and paint finishes are all used. Many colors are available in both chemical and electrochemical finishes. If paint, lacquer or enamel is used, any color possible with these finishes may be applied. Vitreous enamels have been developed for aluminum, and the metal may also be electroplated.

Aluminum sheet, because of its superior corrosion resistance and smooth continuous surface, is an excellent base for the high quality paints used in producing painted sheet. The chemical pretreatment plus the application of high quality thermally cured paint assures a finish that will exhibit no cracking, blistering, or peeling. Accidental damage to products made of painted aluminum sheet will not result in unsightly rust areas or streaks. Experience has shown that paint in the quality used for this product, properly formulated, applied and cured, will show little change in color or loss of gloss after one year's service in the adverse climatic conditions of south-central Florida.

Highly industrialized areas may cause some color change due to atmospheric contaminants.

Proper maintenance can extend the service life considerably—even the finest automobiles require occasional

washing and polishing if they are to retain their original appearance.

Even after many years of service most advantages of the painted sheet remain. It can be repainted with any good grade of house paint with no danger of cracking or peeling, such as is often experienced when paint is applied to other types of base materials.

Painted sheet and the products made from it should be handled with care to avoid damage to the paint film. Repair of large damaged areas is not recommended, but for repair of small areas air drying touch-up paint intended for brush application is available from paint suppliers. Your painted sheet supplier should be contacted for precise information. This touch-up paint cannot be expected to exhibit the same weathering and other characteristics as the original painted sheet, and touched-up areas will present appearance differences after weather exposure. For this reason, use of touch-up paint should be held to a minimum.

Many types of paint systems are used, and it is difficult to establish reasonable and meaningful standards for all of them. Specific applications require consideration of life expectancy, forming requirements and methods, economics, and so forth. Paint systems generally in use exhibit general characteristics as shown on pages 7-31 to 7-33, but for specific applications consult the painted sheet supplier.

These are the characteristics that give aluminum its extreme versatility. In the majority of applications, two or more of these characteristics come prominently into play—for example, light weight combined with strength in airplanes, railroad cars, trucks and other transportation equipment. High resistance to corrosion and high thermal conductivity are important in equipment for the chemical and petroleum industries; these properties combine with nontoxicity for food processing equipment.

Attractive appearance together with high resistance to weathering and low maintenance requirements have led to extensive use in buildings of all types. High reflectivity, excellent weathering characteristics, and light weight are all important in roofing materials. Light weight contributes to low handling and shipping costs, whatever the application.

Many applications require the extreme versatility that only aluminum has. Almost daily its unique combination of properties is being put to work in new ways. The metal now serves as a basic raw material for more than 20,000 businesses scattered throughout the country.

Alloy and Temper Designation Systems for Aluminum (ANSI H35.1 / H35.1(M)-2013)

Information Note: The Aluminum Association is the registrar under ANSI H35.1 / H35.1(M) with respect to the designation and composition of aluminum alloys and tempers registered in the United States, and is also the registrar under an international accord on the composition and designation of registered wrought aluminum alloys. Since there is no international accord on designation and registration of tempers for wrought aluminum alloys and wrought aluminum alloy products, reference to ANSI H35.1 / H35.1(M) properties and characteristics of wrought aluminum alloy tempers registered with the Aluminum Association under ANSI H35.1 / H35.1(M) may not always reflect actual properties and characteristics associated with the particular aluminum alloy temper. The user may wish to confirm that expected properties denoted by specific temper designation(s) are furnished.

NOTE: The user of this Aluminum Standards and Data manual should be aware that the alloy and temper designation systems, as reprinted from ANSI H35.1 / H35.1(M), are those in effect at the time of this manual's publication but are subject to supersession by subsequent revisions of this ANSI standard as it is updated.

1. Scope

This standard provides systems for designating wrought aluminum and wrought aluminum alloys, aluminum and aluminum alloys in the form of castings and foundry ingot, and the tempers in which aluminum and aluminum alloy wrought products and aluminum alloy castings are produced. Specific limits for chemical compositions and for mechanical and physical properties to which conformance is required are provided by applicable product standards.

NOTE: A numerical designation assigned in conformance with this standard should only be used to indicate an aluminum or an aluminum alloy having chemical composition limits identical to those registered with The Aluminum Association and, for wrought aluminum and wrought aluminum alloys, with the signatories of the Declaration of Accord on an International Alloy Designation System for Wrought Aluminum and Wrought Aluminum Alloys.

2. Wrought Aluminum and Aluminum Alloy Designation System ① ② ③ ④ ⑬

A system of four-digit numerical designations is used to identify wrought aluminum and wrought aluminum alloys. The first digit indicates the alloy group as follows:

① Chemical composition limits and designations conforming to this standard for wrought aluminum and wrought aluminum alloys, and aluminum and aluminum alloy castings and foundry ingot may be registered with The Aluminum Association provided: (1) the aluminum or aluminum alloy is offered for sale, (2) the complete chemical composition limits are registered, and (3) the composition is significantly different from that of any aluminum or aluminum alloy for which a numerical designation already has been assigned.

② For codification purposes an alloying element is any element that is intentionally added for any purpose other than grain refinement and for which minimum and maximum limits are specified.

③ Standard limits for alloying elements and impurities are expressed to the following places:

Less than 0.001 percent	0.000X
0.001 but	0.00X
0.01 but less than 0.10 percent	
Unalloyed aluminum made by a refining process	0.0XX
Alloys and unalloyed aluminum not made by a refining process	0.0X
0.10 through 0.55 percent	0.XX
(It is customary to express limits of 0.30 percent through 0.55 percent as 0.X0 or 0.X5)	
Over 0.55 percent	0.X, X.X, etc.
(except that combined Si + Fe limits for 1xxx designations must be expressed as 0.XX or 1.XX)	

Aluminum, 99.00 percent and greater	1xxx
Aluminum alloys grouped by major alloying elements	
Copper	2xxx
Manganese	3xxx
Silicon	4xxx
Magnesium	5xxx
Magnesium and silicon	6xxx
Zinc	7xxx
Other element	8xxx
Unused series	9xxx

The designation assigned shall be in the 1xxx group whenever the minimum aluminum content is specified as 99.00 percent or higher. The alloy designation in the 2xxx through 8xxx groups is determined by the alloying element (Mg₂Si for 6xxx alloys) present in the greatest mean percentage, except in cases in which the alloy being registered qualifies as a modification or variation of a previously registered alloy. If the greatest mean percentage is common to more than one alloying element, choice of group shall be in order of group sequence Cu, Mn, Si, Mg, Mg₂Si, Zn or others.

The last two digits identify the aluminum alloy or indicate the aluminum purity. The second digit indicates modifications of the original alloy or impurity limits.

④ Standard limits for alloying elements and impurities are expressed in the following sequence: Silicon; Iron; Copper; Manganese; Magnesium; Chromium; Nickel; Zinc; Titanium (see Note 1); Other (see Note 2) Elements, Each; Other (see Note 2) Elements, Total; Aluminum (see Note 3).

Note 1—Additional specified elements having limits are inserted in alphabetical order according to their chemical symbols between Titanium and Other Elements, Each, or are listed in footnotes.

Note 2—"Other" includes listed elements for which no specific limit is shown as well as unlisted metallic elements. The producer may analyze samples for trace elements not specified in the registration or specification. However, such analysis is not required and may not cover all metallic "other" elements. Should any analysis by the producer or the purchaser establish that an "other" element exceeds the limit of "Each" or that the aggregate of several "other" elements exceeds the limit of "Total", the material shall be considered non-conforming.

Note 3—Aluminum is specified as minimum for unalloyed aluminum, and as a remainder for aluminum alloys.

⑬ Individual element limits (i.e. a maximum limit or a range) are required for elements having a combined maximum limit in excess of 0.10%. Individual element limits are not required for elements having a combined maximum limit of 0.10% or less.